

INTERNATIONAL
STANDARD

ISO
105-P02

Third edition
2002-09-15

Textiles — Tests for colour fastness —

**Part P02:
Colour fastness to pleating: Steam pleating**

Textiles — Essais de solidité des teintures —

Partie P02: Solidité des teintures au plissage: Plissage à la vapeur

STANDARDSISO.COM : Click to view the full PDF of ISO 105-P02:2002



Reference number
ISO 105-P02:2002(E)

© ISO 2002

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 105-P02:2002

© ISO 2002

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.ch
Web www.iso.ch

Printed in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this part of ISO 105 may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 105-P02 was prepared by Technical Committee ISO/TC 38, *Textiles*, Subcommittee SC 1, *Tests for coloured textiles and colorants*.

This third edition cancels and replaces the second edition (ISO 105-P02:1993), of which it constitutes a minor revision.

ISO 105 was previously published in thirteen "parts", each designated by a letter (e.g. "Part A"), with publication dates between 1978 and 1985. Each part contained a series of "sections", each designated by the respective part letter and by a two-digit serial number (e.g. "Section A01"). These sections are now being republished as separate documents, themselves designated "parts" but retaining their earlier alphanumeric designations. A complete list of these parts is given in ISO 105-A01.

Textiles — Tests for colour fastness —

Part P02: Colour fastness to pleating: Steam pleating

1 Scope

1.1 This part of ISO 105 specifies a method for determining the resistance of the colour of textiles of all kinds and in all forms to the action of steam-pleating processes. The materials are not pleated during the test, and it is emphasized that the test is not intended for assessing the quality of the pleating process.

1.2 Three tests differing in severity are provided; one or more of them may be used depending on the requirements.

2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this part of ISO 105. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this part of ISO 105 are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 105-A01:1994, *Textiles — Tests for colour fastness — Part A01: General principles of testing*

ISO 105-A02:1993, *Textiles — Tests for colour fastness — Part A02: Grey scale for assessing change in colour*

ISO 105-A03:1993, *Textiles — Tests for colour fastness — Part A03: Grey scale for assessing staining*

ISO 105-F:1985, *Textiles — Tests for colour fastness — Part F: Standard adjacent fabrics*

ISO 105-F10:1989, *Textiles — Tests for colour fastness — Part F10: Specification for adjacent fabric: Multifibre*

ISO 139:1973, *Textiles — Standard atmospheres for conditioning and testing*

3 Principle


A specimen of the textile in contact with either one or two specified adjacent fabrics is steamed under pressure and dried. The change in colour of the specimen, and the staining of the adjacent fabric(s), are assessed with the grey scales.

4 Apparatus and materials

4.1 Specimen holder (see Figure 1), consisting of a copper tube 80 mm in external diameter. The thickness of the copper is 1,5 mm. The copper tube is wrapped with six layers of bleached cotton fabric of mass per unit area approximately 125 g/m², on which the test specimen is wrapped. Wrapped round the test specimen is an outer

cover made from bleached cotton fabric of mass per unit area approximately 185 g/m². The outer cover is held in place by rods made from 6-mm-diameter mild steel, spring-fitted to the tube.

The strength of the springs is not critical, but it shall be sufficient to hold the cover tightly against the tube. The springs are conveniently fastened to one of the rods and should hook easily on to the other.

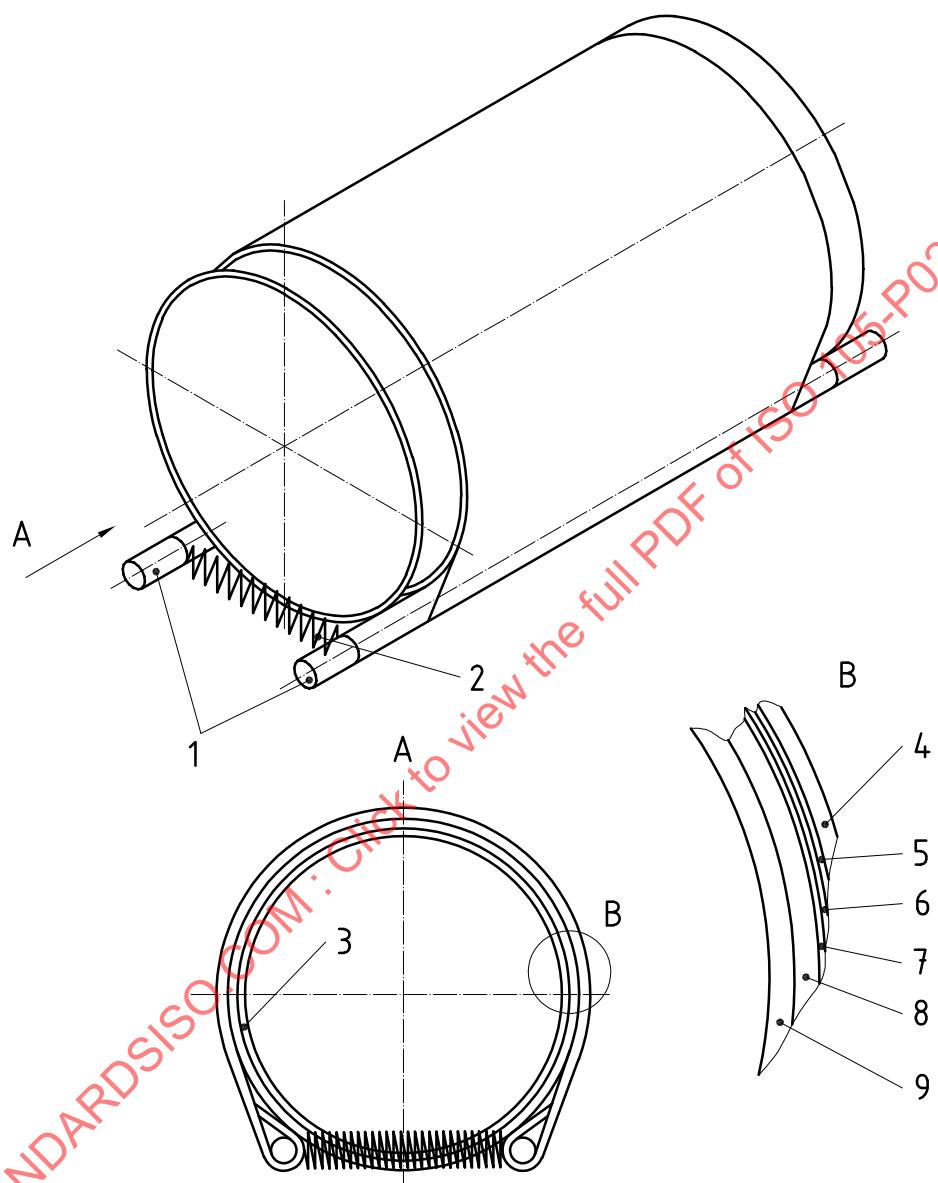

Key

1 Steel rods	6 Specimen
2 Spring to hold steel rods in place at both ends of cylinder	7 Adjacent fabric
3 Copper cylinder (80 mm diameter, 1,5 mm thick)	8 Six layers of cotton fabric
4 Outer cover of cotton fabric	9 Copper cylinder
5 Adjacent fabric	

Figure 1 — Specimen holder

4.2 Jacketed steamer or pressure cooker.

Use

- a) a jacketed steamer designed so that the pressure can be accurately determined and that no water splashes on to the specimen during test;
- or
- b) a domestic pressure cooker sufficiently large to avoid water splashing on to the specimen during the test; the minimum size shall be 230 mm in diameter and 260 mm high, and it shall be fitted with an accurate pressure gauge. A domestic pressure cooker shall not be used for the severe test.

The specimen holder (4.1) shall be loosely wrapped in one layer of polyester film which projects 10 mm over each end of the tube and is not closed at the ends.

The specimen holder shall be placed in a rectangular metal container containing ten 1 mm holes equally spaced along the centre of the bottom. The container shall be sufficiently deep to reach to 10 mm from the top of the specimen holder (see Figure 2). The bottom of the container shall be slightly concave to ensure that condensed water drains away rapidly. The container shall be placed on a stand which holds it 50 mm above the surface of the water.

NOTE The quantity of water in the cooker is not critical, but water to a depth of 30 mm is suggested.

Expel air from the pressure cooker for 2 min before raising the pressure.

4.3 Adjacent fabrics (see ISO 105-A01:1994, subclause 8.3).

NOTE If wool is used as one of the adjacent fabrics, it may have an adverse effect on the dye in the specimen, particularly under alkaline conditions.

Either:

4.3.1 A multifibre adjacent fabric, complying with ISO 105-F10.


Or:

4.3.2 Two single-fibre adjacent fabrics, complying with the relevant sections of F01 to F08 of ISO 105-F:1985, each measuring 40 mm × 50 mm and made of the same kind of fibre as that of the textile to be tested, or as otherwise specified. In the case of blends, two different adjacent fabrics are required, corresponding to the two predominant fibres of the specimen.

4.4 If required, a **non-dyeable fabric** (for example, polypropylene).

4.5 **Grey scale for assessing change in colour**, complying with ISO 105-A02, and **grey scale for assessing staining**, complying with ISO 105-A03.

Dimensions in millimetres

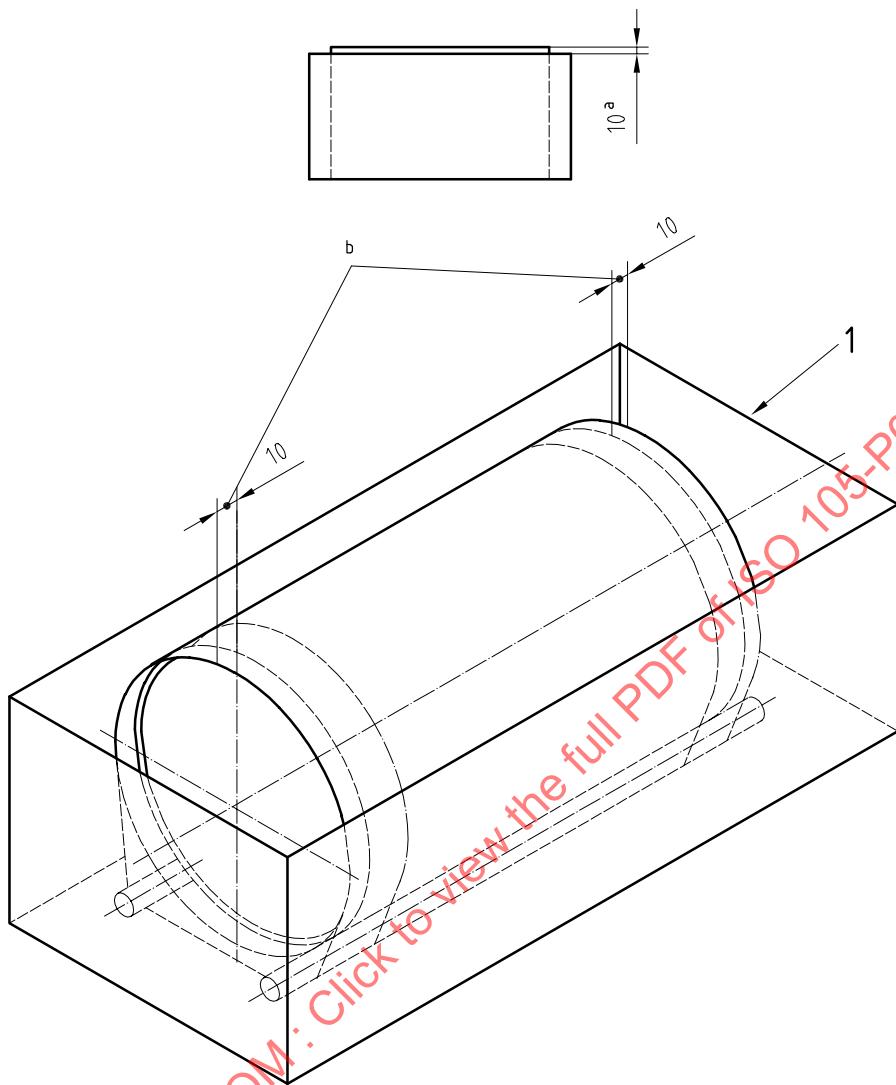**Key**

1 Metal container

NOTE Ten 1-mm-diameter holes shall be drilled in bottom of container, equally spaced.

a Top of cylinder to project 10 mm above top of container.

b Polyester film to overlap copper cylinder by 10 mm at both ends.

Figure 2 — Specimen holder in container

5 Test specimen

5.1 If the textile to be tested is fabric,

- a) attach a specimen measuring 40 mm × 100 mm to a piece of the multifibre adjacent fabric (4.3.1), also measuring 40 mm × 100 mm, by sewing along one of the shorter sides, with the multifibre fabric next to the face of the specimen;
 - or
- b) attach a specimen measuring 40 mm × 100 mm between the two single-fibre adjacent fabrics (4.3.2), also measuring 40 mm × 100 mm, by sewing along one of the shorter sides.

5.2 Where yarn or loose fibre is to be tested, take a mass of the yarn or loose fibre approximately equal to one-half of the combined mass of the adjacent fabrics and

- a) place it between a 40 mm × 100 mm piece of the multifibre adjacent fabric and a 40 mm × 100 mm piece of the non-dyeable fabric (4.4) and sew them along all four sides (see ISO 105-A01:1989, subclause 9.6);
 - or
- b) place it between a 40 mm × 100 mm piece of each of the two specified single-fibre fabrics and sew along all four sides.

6 Procedure

6.1 Mount the composite specimen in the holder (4.1) as shown in Figure 1.

6.2 Place the holder containing the composite specimen in a jacketed steamer (all tests) or pressure cooker (mild and intermediate tests only). A pressure cooker shall not be used for the severe test. A jacketed steamer shall be used for the severe test.

6.3 Steam under one of the conditions given in Table 1.

6.4 When steaming is complete, release the pressure over a period not exceeding 2 min.

6.5 Open out the composite specimen and dry it by hanging it in air at a temperature not exceeding 60 °C with the three parts in contact only at one line of stitching. Condition for 4 h in air in the standard temperature atmosphere for testing as defined in ISO 139, i.e. a temperature of 20 °C ± 2 °C and relative humidity of (65 ± 2) %. In tropical countries, the standard tropical atmosphere for testing as defined in ISO 139 may be used, i.e. a temperature of 27 °C ± 2 °C and relative humidity of (65 ± 2) %.

6.6 Assess the change in colour of the specimen and the staining of the adjacent fabric with the grey scales (4.5).

6.7 Specimens which liberate formaldehyde under steam-pleating conditions shall be tested separately.

NOTE It should be noted that the papers used in commercial pleating occasionally contain reducing agents which, with certain types of colouring matter, can produce a much greater change in colour than occurs under the test conditions.