

---

---

**Clothing for protection against heat  
and flame — Determination of contact  
heat transmission through protective  
clothing or constituent materials —**

**Part 1:  
Contact heat produced by heating  
cylinder**

*Vêtements de protection contre la chaleur et la flamme —  
Détermination de la transmission thermique par contact à travers les  
vêtements de protection ou leurs matériaux constitutifs —*

*Partie 1: Transmission thermique par contact produite par un  
cylindre chauffant*



STANDARDSISO.COM : Click to view the full PDF of ISO 12127-1:2015



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

# Contents

|                                                                                                | Page     |
|------------------------------------------------------------------------------------------------|----------|
| Foreword.....                                                                                  | iv       |
| Introduction.....                                                                              | v        |
| <b>1 Scope.....</b>                                                                            | <b>1</b> |
| <b>2 Terms and definitions.....</b>                                                            | <b>1</b> |
| <b>3 Principle.....</b>                                                                        | <b>1</b> |
| <b>4 Apparatus.....</b>                                                                        | <b>2</b> |
| <b>5 Sampling and conditioning.....</b>                                                        | <b>2</b> |
| 5.1 Sampling.....                                                                              | 2        |
| 5.2 Conditioning.....                                                                          | 3        |
| <b>6 Test method.....</b>                                                                      | <b>3</b> |
| 6.1 Starting conditions.....                                                                   | 3        |
| 6.2 Procedure.....                                                                             | 3        |
| 6.3 Evaluation.....                                                                            | 3        |
| <b>7 Test report.....</b>                                                                      | <b>3</b> |
| <b>Annex A (informative) Best practices for cleaning the heating cylinder.....</b>             | <b>8</b> |
| <b>Annex B (normative) Determination of property values for rating and classification.....</b> | <b>9</b> |

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

ISO 12127-1 was prepared by Technical Committee ISO/TC 94, *Personal safety — Protective clothing and equipment*, Subcommittee SC 13, *Protective clothing*, and by Technical Committee CEN/TC 162, *Protective clothing including hand and arm protection and lifejackets* in collaboration.

This second edition cancels and replaces the first edition (ISO 12127-1:2007), of which it constitutes a minor revision. The following changes have been made:

- a) title, for better comprehension;
- b) alphabetical order, "Terms and definitions";
- c) modified clause for "Heating cylinder" regarding example and pictures;
- d) modified clause for "Calorimeter" regarding more detailed information;
- e) modified clause for "Assembly" regarding speed and picture;
- f) latest standard numbers in clause "Test report";
- g) new [Annex A](#) for "Best practices for cleaning the heating cylinder";
- h) new [Annex B](#) for "Determination of property values for rating and classification".

ISO 12127 consists of the following parts, under the general title *Clothing for protection against heat and flame — Determination of contact heat transmission through protective clothing or constituent materials*:

- *Part 1: Contact heat produced by heating cylinder*
- *Part 2: Test method using contact heat produced by dropping small cylinders*

## Introduction

Protective clothing designed to protect against heat and flame can be exposed to direct contact with hot substances or hot surfaces.

The diversity of such contact conditions makes it difficult to evaluate the hazards that can arise from high temperature.

The test method described in this part of ISO 12127 allows this heat transfer to be assessed when a heating cylinder and the clothing material are brought into contact with each other.

This part of ISO 12127 forms part of a series of standards concerned with clothing designed to protect against heat and fire.

STANDARDSISO.COM : Click to view the full PDF of ISO 12127-1:2015

STANDARDSISO.COM : Click to view the full PDF of ISO 12127-1:2015

# Clothing for protection against heat and flame — Determination of contact heat transmission through protective clothing or constituent materials —

## Part 1: Contact heat produced by heating cylinder

### 1 Scope

This part of ISO 12127 specifies a test method for the determination of contact heat transmission. It is applicable to protective clothing (including hand protectors) and its constituent materials intended to protect against high contact temperatures.

Application of this part of ISO 12127 is restricted to contact temperatures between 100 °C and 500 °C.

### 2 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

#### 2.1

##### **contact force**

force acting on the test specimen and the calorimeter when they have been brought into contact with the heating cylinder

#### 2.2

##### **contact temperature**

$T_c$

surface temperature of the contact area of the heating cylinder, this temperature being kept constant

#### 2.3

##### **rate of contact**

relative speed with which the heating cylinder and the calorimeter with the test specimen are brought into contact with each other

#### 2.4

##### **start of timing**

moment when the upper surface of the calorimeter and the bottom edge of the heating cylinder are within 10 mm of each other

#### 2.5

##### **threshold time**

$t_t$

time between the start of timing and the moment when the temperature of the calorimeter is 10°C above its starting value

### 3 Principle

The heating cylinder is heated to and maintained at the contact temperature and a test specimen is placed on the calorimeter. The heating cylinder is lowered onto the test specimen supported by the calorimeter or, alternatively, the calorimeter with the specimen is lifted up to the heating cylinder. In either case, the operation is carried out at a constant speed. The threshold time is determined by monitoring the temperature of the calorimeter.

## 4 Apparatus

### 4.1 Heating cylinder

The heating cylinder shall be constructed from a suitable metal which can withstand temperatures of over 500°C (e.g. Silver Alloy, 925 Sterling Silver). Figures 1, 2 and 3 show an example of the stamp and heating cylinder. The contact surface shall have a diameter of  $(25,2 \pm 0,05)$  mm and shall be polished. There shall be a central boring which ends 2 mm above the lower surface of the heating cylinder. This boring is intended to hold the temperature sensor, which is necessary for regulation of the temperature of the heating cylinder, and its diameter should be chosen accordingly. The heating cylinder shall be enclosed by heat-resistant insulation, leaving free the bottom contact surface.

The heating cylinder shall be capable of being heated to over 500°C and be capable of maintaining the chosen testing temperature.

### 4.2 Calorimeter

The calorimeter (as shown in Figure 4) consists of a cylindrical disc of black anodized pure aluminium of  $(25 \pm 0,05)$  mm diameter, and thickness of approximately 5.0 mm and a mass of  $(6,63 \pm 0,03)$  g, which is pushed into a mounting made from polyamide 6.6 so as to be a tight fit. The upper contact surface of the disc shall be surface ground before anodization and shall have a thermocouple attached to its lower surface by means of adhesive tape.

NOTE A PR 6462 BK/02 Thermocoax thermocouple or equivalent has been found to be suitable.<sup>1)</sup>

### 4.3 Assembly

Figure 5 shows an example of the assembly. The heating cylinder and calorimeter are mounted with parallel faces and with their symmetrical axes in line in a supporting frame. Provision shall be made for moving at a controlled speed  $(5,0 \pm 0,5)$  mm/s either the heating cylinder down towards the calorimeter or the calorimeter up towards the heating cylinder. An additional weight shall be dimensioned in such a way that the contact force is  $(49 \pm 0,5)$  N. Between measurement, during cooling periods, a suitable shielding shall be put between the heating cylinder and the calorimeter in order to prevent the calorimeter from being heated by thermal radiation from the heating cylinder.

### 4.4 Electronic devices

Suitable electronic devices shall be provided to

- raise the temperature of the heating cylinder to the chosen testing temperature and maintain this temperature to  $\pm 2^\circ\text{C}$ ;
- control the rate of contact;
- measure and register the calorimeter temperature to an accuracy of  $\pm 0,1^\circ\text{C}$ ;
- measure the threshold time.

## 5 Sampling and conditioning

### 5.1 Sampling

Three circular test specimens of 80 mm diameter shall be taken for each contact temperature from the product or from a piece of the material intended for manufacture of the product. If one specimen fails the performance standard a further set of three specimens shall be tested (see [Annex B](#)).

1) This is an example of a suitable product available commercially. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of this product.



## 5.2 Conditioning

Before testing, textile specimens shall be conditioned for at least 24 h and leather specimens for at least 48h in an atmosphere having a temperature of  $(20 \pm 2) ^\circ\text{C}$  and relative humidity of  $(65 \pm 5) \%$ .

## 6 Test method

### 6.1 Starting conditions

The measurements shall be carried out in an environment having a temperature of  $(20 \pm 5) ^\circ\text{C}$  and relative humidity between 15 % and 80 %. The heating cylinder shall be brought to  $\pm 2 \%$  of the selected contact temperature (in degrees Celsius). The temperature of the calorimeter shall be at room temperature  $\pm 2^\circ\text{C}$  before the start of each test. The test shall be started not later than 3 min after the test specimen has been taken out of the conditioning atmosphere (see 5.2).

### 6.2 Procedure

Place the test specimen on the calorimeter so that its outer face is upwards. Remove the shielding between the heating cylinder and the calorimeter and bring the heating cylinder into contact with the calorimeter at a rate of contact of  $(5,0 \pm 0,2) \text{ mm/s}$ . Measure and record the temperature of the calorimeter during the test. Carry out at least three measurements at each contact temperature.

### 6.3 Evaluation


Determine the threshold time,  $t_t$ , to the nearest 0,1 s.

## 7 Test report

The test report shall contain the following elements:

- a) reference to ISO 12127-1;
- b) name of the supplier of the product or material;
- c) name, as given by the supplier, and description of the product or material;
- d) contact temperature(s),  $T_c$ ;
- e) threshold time,  $t_t$ , for each individual specimen per contact temperature, the mean value and standard deviation. The uncertainty of measurement of the threshold time  $t_t$  shall be given in the report.
- f) description of observed changes in the test specimens;
- g) date of test.


Dimensions in millimetres

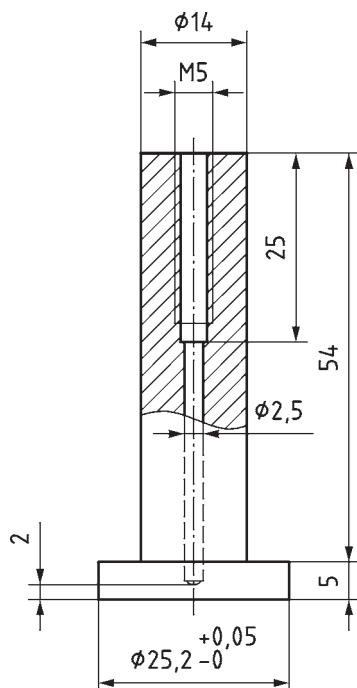

Heating Element: e.g. Silver Alloy, 925 Sterling Silver

**Figure 1 — Stamp**

Dimensions in millimetres

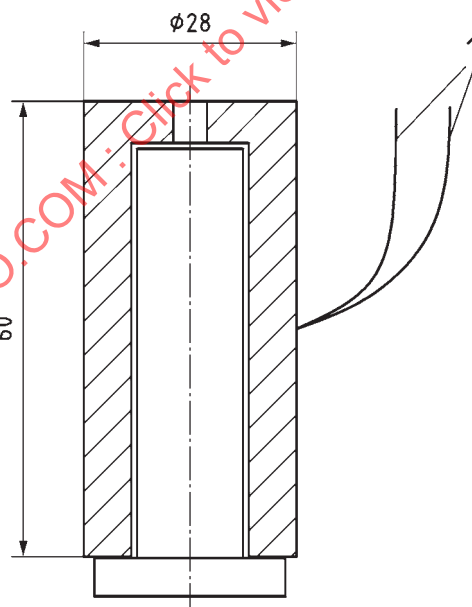


**Key**

1

connector

Heating Element with Heater, Example: Ersa Type 201 200 W

**Figure 2 — Heat cylinder with stamp**

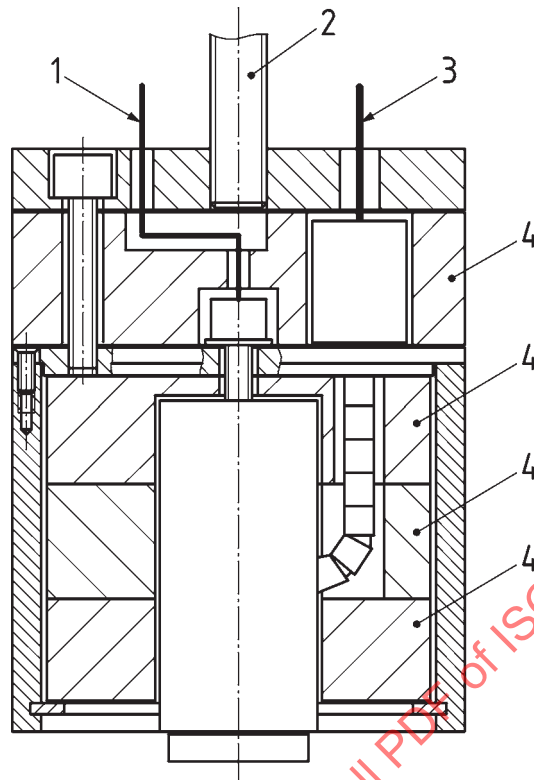


**Key**

- 1 thermocouple
- 2 mounting screw
- 3 connector
- 4 heating isolation

**Figure 3 — Heating cylinder with stamp built in encased insulating material**

Dimensions in millimetres

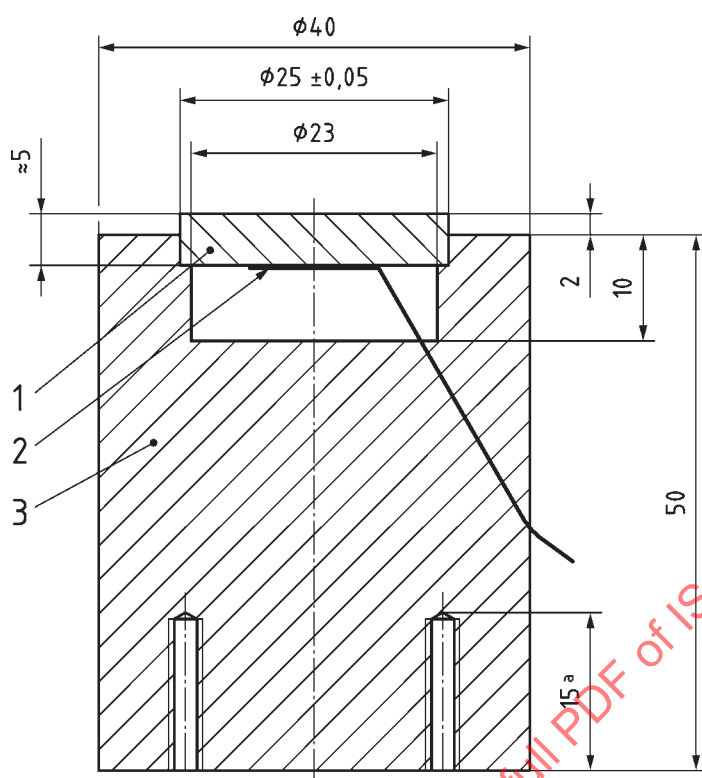

**Key**

- 1 cylindrical disc, made from black anodized pure aluminium
- 2 thermocouple
- 3 mounting, made from polyamide 6.6
- a Maximum depth of thread holes for mounting the calorimeter.

**Figure 4 — Calorimeter**