

---

---

**Reinforcement products — Mats and  
fabrics — Determination of mass per unit  
area**

*Renforts — Mats et tissus — Détermination de la masse surfacique ou  
grammage*

STANDARDSISO.COM : Click to view the full PDF of ISO 3374:2000



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 3374:2000

© ISO 2000

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.ch](mailto:copyright@iso.ch)  
Web [www.iso.ch](http://www.iso.ch)

Printed in Switzerland

## Contents

	Page
Foreword.....	iv
1 Scope .....	1
2 Normative references .....	1
3 Term and definition .....	1
4 Principle.....	1
5 Apparatus .....	2
6 Test specimens.....	2
7 Conditioning and test atmospheres .....	3
8 Procedure .....	5
9 Calculation and expression of results.....	5
10 Test report .....	5
Annex A (informative) Precision and bias .....	6

STANDARDSISO.COM : Click to view the full PDF of ISO 3374:2000

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this International Standard may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 3374 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 13, *Composites and reinforcement fibres*.

This third edition cancels and replaces the second edition (ISO 3374:1990), which has been technically revised.

Annex A of this International Standard is for information only.

STANDARDSISO.COM : Click to view the full PDF of ISO 3374:2000

# Reinforcement products — Mats and fabrics — Determination of mass per unit area

## 1 Scope

This International Standard specifies a method for determining the mass per unit area of mats (either chopped-strand mat or continuous-strand mat) or fabrics which may be manufactured with glass or carbon or aramid yarns.

## 2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this International Standard. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 291:1997, *Plastics — Standard atmospheres for conditioning and testing*.

ISO 3344:1997, *Reinforcement products — Determination of moisture content*.

ISO 5725-1:1994, *Accuracy (trueness and precision) of measurement methods and results — Part 1: General principles and definitions*.

ISO 5725-2:1994, *Accuracy (trueness and precision) of measurement methods and results — Part 2: Basic method for the determination of repeatability and reproducibility of a standard measurement method*.

## 3 Term and definition

For the purposes of this International Standard, the following term and definition apply:

### 3.1

#### **mass per unit area**

the ratio of the mass of a piece of mat or fabric of specified dimensions to the area

NOTE This mass includes both the strands and any other material protecting or binding the strands or yarns.

## 4 Principle

The mass of a test specimen of known area is determined, and the mass per unit area calculated.

## 5 Apparatus

### 5.1 Polished metal template, which yields a test specimen with

- a square shape of area 1 000 cm<sup>2</sup> for mats;
- a square or circular shape of area 100 cm<sup>2</sup> for fabrics.

The permissible error in the area of the resulting specimens shall be 1 % or less.

By agreement between the interested parties, a larger specimen may be used. In such cases, the shape and dimensions of the specimen shall be noted in the test report.

### 5.2 Suitable cutting tool, for example knife, scissors, cutting disc or punch.

**5.3 Specimen holder**, which provides optimum air circulation around the specimen, made from a heat-resistant material and such that there is no loss of the product under test. This may be a basket constructed from stainless-steel wire mesh.

### 5.4 Balance, having the following characteristics:

Material	Measuring capability	Limit of permissible error	Resolution
Mats, all weights	0 to 150 g	0,5 g	0,1 g
Fabrics $\geq$ 200 g/m <sup>2</sup>	0 to 150 g	10 mg	1 mg
Fabrics < 200 g/m <sup>2</sup>	0 to 150 g	1 mg	0,1 mg

In cases where larger specimens are taken (see 5.1), a balance shall be used that provides equivalent accuracy.

### 5.5 Apparatus to be used in cases when specimens must be dried:

**5.5.1 Ventilated drying oven**, with an air change rate of 20 to 50 times per hour, capable of maintaining a temperature of 105 °C  $\pm$  3 °C.

**5.5.2 Desiccator**, containing a suitable drying agent (for example silica gel, calcium chloride or phosphorus pentoxide).

**5.5.3 Stainless-steel tongs**, for handling the specimen and specimen holder.

## 6 Test specimens

Unless otherwise agreed between the interested parties, the number of specimens taken from each roll or from the laboratory sample shall be

for mats: three 1 000 cm<sup>2</sup> specimens per metre of width (in practice, normally one specimen for every 31,6 cm across the width of the mat);

for fabrics: one 100 cm<sup>2</sup> specimen per 50 cm of width.

In all cases, a minimum of two specimens shall be taken.

Suggested methods for cutting specimens are shown in Figure 1 for mats and Figures 2 and 3 for fabrics.

Note that

for mats:

- specimens are taken in one row, generally side by side,
- the distance from the edge may be zero for trimmed mats, but the distance from any untrimmed edges shall be at least 10 cm;

for fabrics:

- specimens are taken separately, preferably involving different weft yarns,
- the distance from the edge/selvedge shall be at least 5 cm.

Special instructions shall be provided, as needed, to the operators to assure that the cutting procedure results in specimens areas which are within the tolerance range for this method.

For mats narrower than 31,6 cm and fabrics narrower than 25 cm, the specimen type and dimensions shall be agreed between the purchaser and supplier.


NOTE Some specifications may stipulate that the mass per unit area is based on a method using the whole roll as the test specimen. In that case, the mass of the roll is divided by the full area of the roll.

The result obtained (in these specifications, usually called the "actual mean weight") is not necessarily comparable with that obtained with the method described in this International Standard.

## 7 Conditioning and test atmospheres

Unless otherwise specified in the product specification or by the person ordering the test, no conditioning of the specimens is required.


If conditioning is utilized, refer to ISO 291.

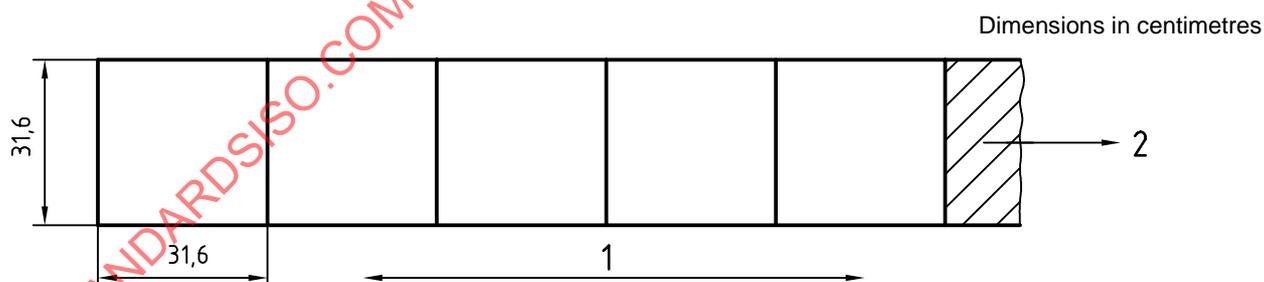

### Key

- 1 Direction of mat width
- 2 Discard


Figure 1 — Suggested method for cutting out mat specimens

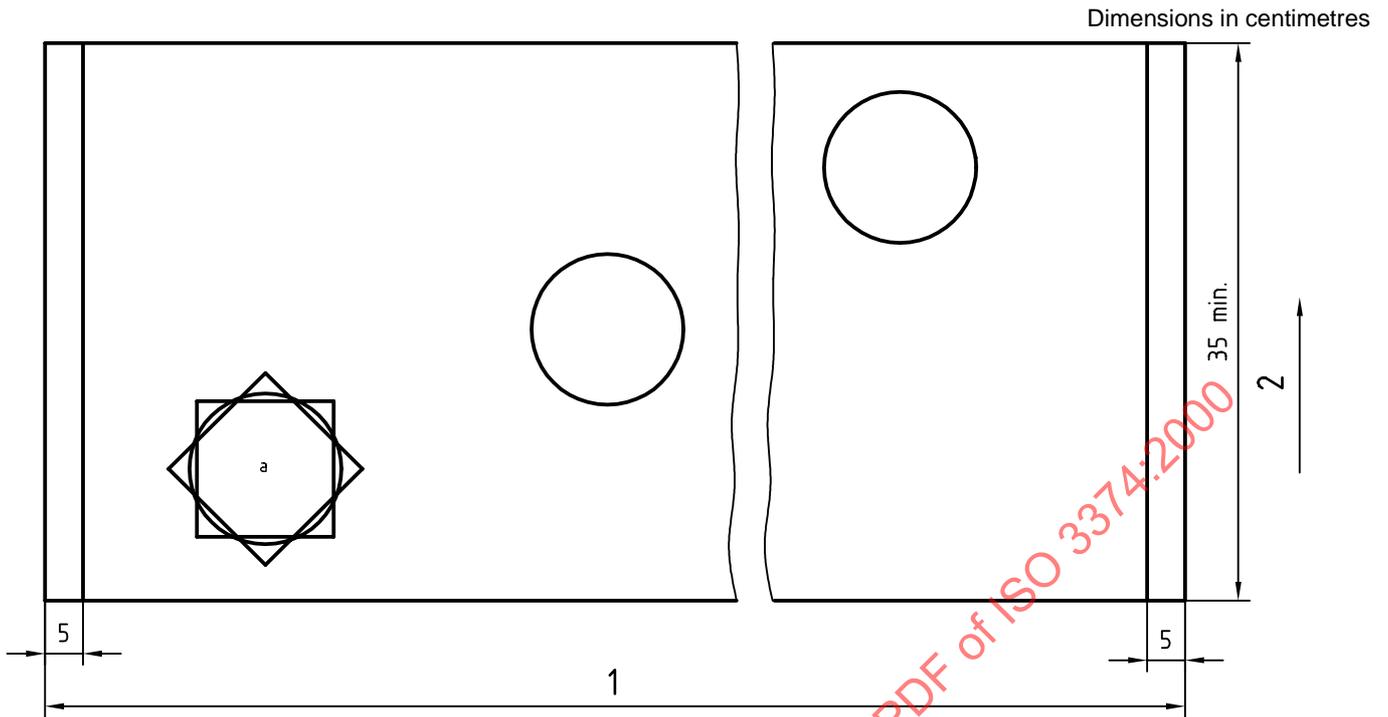

**Key**

- 1 Width of fabric
- 2 Warp direction
- a Instead of circular specimens, square specimens may be taken oriented either parallel to or diagonally across the yarns.

**Figure 2 — Suggested method for cutting out fabric specimens (fabrics wider than 50 cm)**

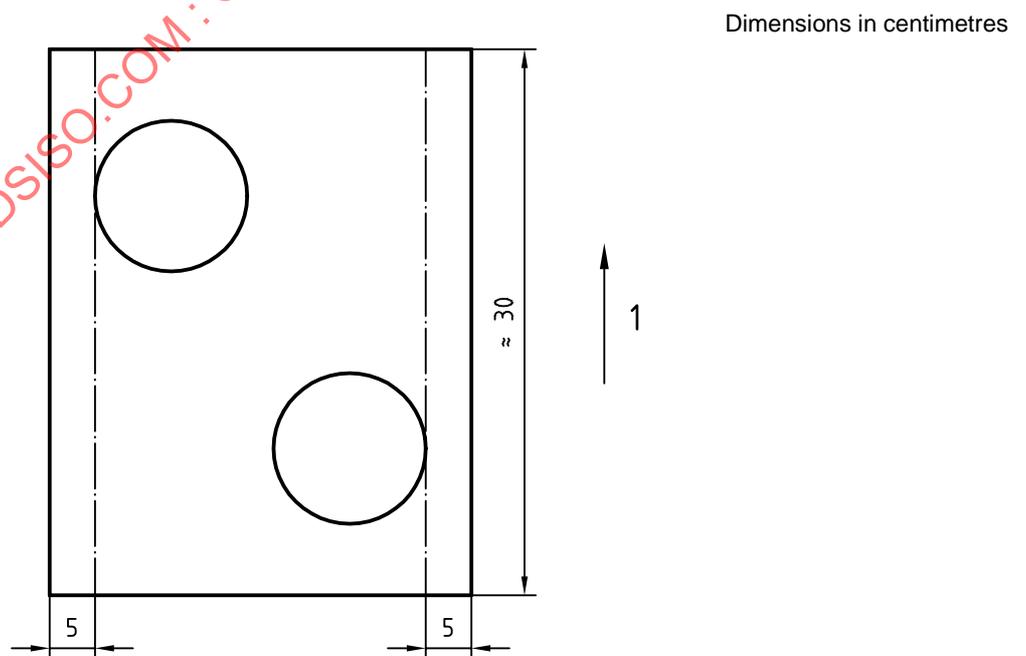

**Key**

- 1 Warp direction

**Figure 3 — Suggested method for cutting out fabric specimens (fabrics between 25 cm and 50 cm wide)**

## 8 Procedure

8.1 Cut a strip at least 35 cm wide across the entire width of the mat or fabric as the laboratory sample.

8.2 Using the cutting tool (5.2) and template (5.1) and a clean work surface, cut the number of specimens specified in clause 6.

If the test specimens have fibres that may be lost, utilize a holder (5.3) and, if necessary, fold the specimens, taking care to keep all strands or yarns.

8.3 Unless otherwise agreed between the interested parties, dry the specimens in a ventilated oven (5.5.1) at  $105\text{ °C} \pm 3\text{ °C}$  for 1 h in cases when the mat or fabric contains more than 0,2 % moisture (or if the moisture content is unknown), then remove to a desiccator (5.5.2) and cool to room temperature. Upon removal from the desiccator, proceed to step 8,4 immediately.

8.4 Weigh each test specimen and record the result, subtracting the tare if a specimen holder was used.

The accuracy to which this mass is recorded shall correspond to the sensitivity of the balance (see 5.4).

## 9 Calculation and expression of results

9.1 For each specimen, calculate the mass per unit area  $\rho_A$ , in grams per square metre, using the equation

$$\rho_A = 10\,000 \times \frac{m_s}{A}$$

where

$m_s$  is the mass, in grams, of the specimen;

$A$  is the area, in square centimetres, of the specimen.

9.2 Report the mass per unit area as the average value for all the specimens taken across the width of the mat or fabric.

Give the result to the nearest 1 g/m<sup>2</sup> for mats and fabrics weighing 200 g/m<sup>2</sup> or more and to the nearest 0,1 g/m<sup>2</sup> for fabrics lighter than 200 g/m<sup>2</sup>.

Optionally, specifications or persons ordering the test may also require that the results for each individual specimen be reported, as such data may yield information about the mass distribution across the material.

## 10 Test report

The test report shall include the following particulars:

- a) a reference to this International Standard;
- b) all details necessary for complete identification of the mat or fabric tested;
- c) the mass per unit area of the mat or fabric (optionally, or if required, the result for each individual specimen may also be reported);
- d) details of any operation not specified in this International Standard, as well as any information or details of any incident liable to have a bearing on the results (for instance, the number of specimens used, whether or not preliminary drying of the specimens was necessary or whether specimens different from those specified were used);
- e) the date of the test.