



SURFACE VEHICLE STANDARD	J1277™	AUG2024
	Issued 1982-05 Reaffirmed 2018-10 Revised 2024-08	
Superseding J1277 OCT2018		
Method for Assessing the Cleanliness Level of New Hydraulic Fluid		

RATIONALE

Changes in this document were to add clarity to the agitation procedure in 4.1.

1. SCOPE

To provide a method by which to assess the cleanliness of new hydraulic fluids. The method is applicable to new mineral and synthetic hydraulic fluids - regardless of packaging. This SAE Standard is not intended as a procedure for operating equipment.

1.1 Purpose

To establish a quality control procedure suitable for both users and producers by which the cleanliness level of new hydraulic fluid can be quantified, certified, and specified.

2. REFERENCES

2.1 Applicable Documents

The following publications form a part of this specification to the extent specified herein. Unless otherwise indicated, the latest issue of SAE publications shall apply.

2.1.1 ASTM Publications

Available from ASTM International, 100 Barr Harbor Drive, P.O. Box C700, West Conshohocken, PA 19428-2959, Tel: 610-832-9585, www.astm.org.

ASTM D4057 Method for Manual Sampling of Petroleum Products

ASTM D6304 Method of Test for Water in Liquid Petroleum Products by Karl Fischer Reagent

2.1.2 ISO Publications

Copies of these documents are available online at <https://webstore.ansi.org/>.

ISO 3722 Hydraulic fluid power - Fluid sample containers - Qualifying and controlling cleaning methods

SAE Executive Standards Committee Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2024 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system, transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, or used for text and data mining, AI training, or similar technologies, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Tel: +1 724-776-4970 (outside USA)
Fax: 724-776-0790
Email: CustomerService@sae.org
SAE WEB ADDRESS: <http://www.sae.org>

For more information on this standard, visit
https://www.sae.org/standards/content/J1277_202408/

- ISO 4406 Hydraulic fluid power - Fluids - Method for coding the level of contamination by solid particles
- ISO 11171 Hydraulic fluid power - Calibration of automatic particle counters for liquids
- ISO 11500 Hydraulic fluid power - Determination of the particulate contamination level of a liquid sample by automatic particle counting using the light-extinction principle

3. MATERIALS AND APPARATUS

- 3.1 Use an appropriate means of agitating the fluid in its normal storage container (for example, a paint shaker for small containers, a drum rocker for large shipping containers, and a high-volume circulating system for bulk storage vessels).
- 3.2 Use a device to facilitate the withdrawal of a fluid specimen at the prescribed level in the container. Examples of such devices are illustrated in Figure 1 - a bottle thief (refer to ASTM D270) for tanks, a drum sampler, and a crankcase sample for cans.
- 3.3 Use a clean opener to provide an access hole in small containers. In larger vessels, appropriate openings usually exist.
- 3.4 Use sample bottles containing less than 15 particles/mL of bottle volume greater than 5 μm in size as qualified per ISO 3722. The sample bottles shall be large enough in size to contain enough fluid to run at least four tests.
- 3.5 Use an automatic particle counter calibrated per ISO 11171.

4. SAMPLING PROCEDURE

- 4.1 Agitate the fluid in the container using an appropriate means such as suggested in 3.1. Agitate until the fluid in the container is homogeneous before taking a sample.
- 4.2 Clean the area around the location for the access hole with a lint-free cloth that is visibly free of dirt.
- 4.3 Open the container and insert the sampling device as suggested in 3.2, where its fluid entrance is well below the surface, and extract a volume of fluid equal to at least five times, preferably 10 times, the total sampling apparatus volume for the purpose of flushing the wetted surfaces. This hydraulic fluid may be discarded or returned to the container. Care should be taken to keep the external surfaces of the sampling device that is inserted into the container free from contaminant prior to and during sampling.
- 4.4 After the flushing volume has been removed, insert the sampling appendage to within 5% from the bottom of the vessel and withdraw a sufficient amount of fluid to run four analyses into the sample container.

NOTE 1: Where appropriate, the sample should be taken with the container tilted approximately 30 degrees from the vertical such that the opening through which the sample is taken is on a vertical line passing through the lowest point of the vessel.

NOTE 2: When using the bottle thief, the cork should not be opened for at least 30 seconds to allow particles on external surfaces to settle past the bottle.

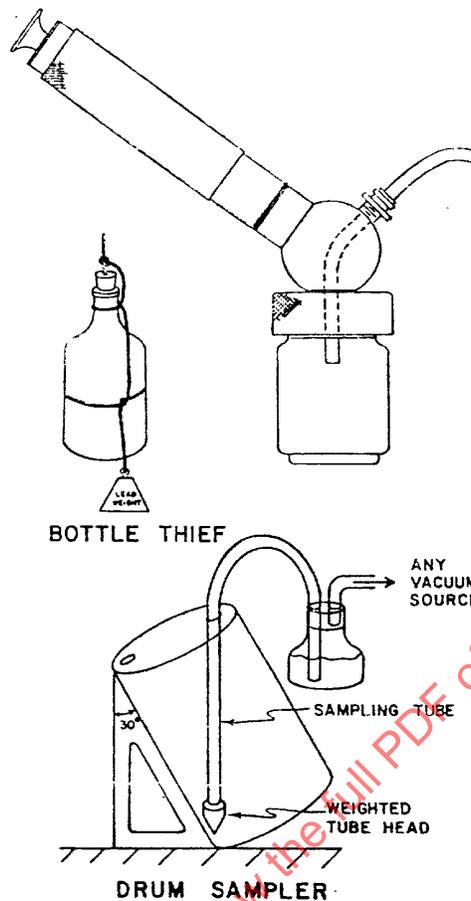


Figure 1 - Withdrawal devices

5. SAMPLE ANALYSIS

- 5.1 Using an automatic particle counter (APC) calibrated as specified in 3.5, count and record the number of particles in at least 10 mL of fluid in the following size ranges: numbers greater than 4, 6, and 14 μm . Repeat at least three times. The first analysis is to be considered a “flushing” procedure to cleanse the APC and is not to be included in the final results. Discard these results and run the next three analyses to use as particle count data. The final three analysis runs are to be averaged into a final result.
- 5.2 The average of three different counts from the same sample should be reported.

6. PRESENTATION OF RESULTS

- 6.1 The raw data from each analysis run should be reported in tabular format to clearly display the particle count for each level, i.e., 4, 6, and 14 μm . The cleanliness code should also be displayed per ISO 4406 as the average of all three analysis runs, i.e., 23/17/14. Additional displays or plots can be provided as instructed by the customer.

7. INTERPRETATION OF RESULTS

- 7.1 Results displayed are purely for clear, concise communication to the customer as to the condition of the new oil. No interpretations or conclusions will be drawn as part of this standard as each customer may have different cleanliness goals.